

UTILIZING E-WASTE AND MARBLE DUST IN CONCRETE: EXPERIMENTAL STUDY AND ANALYSIS

*IJARAPULA MOHAN, 2AAKUTHOTA SRINIVAS, 3GAJULA NAGAMANI, 4DODDI
SRINATH*

*1234Assistant Professor
Department Of Civil Engineering
Samskruti College of Engineering and Technology, Hyderabad*

ABSTRACT

The work was conducted on M20 grade mix. The replacement of coarse aggregate with E-waste in the range of different percentages (0%, 5%, 10%, 15%, 20%, 25%, 30%, 35%) and 15% replacement of cement with marble dust. Finally, the fresh and harden properties of concrete mix specimens obtained from the addition of these materials are compared with control concrete mix. The test results shows that a proper improvement in compressive strengths were achieved in the E-waste and marble dust concrete compared to conventional concrete and can be used effectively in concrete. The reuse of E-waste leads in waste reduction and resources conservation.

Keywords: Ewaste (Electronic waste), M20 grade mix, marble dust, compressive strengths.

1. INTRODUCTION

Waste management is typically dealt depending on the type of waste, quantity of waste generated and the degree of associated problems with the environment. It is believed that recycling of industrial wastes is technically economical and also has several environmental benefits. Wastes from the industries can be used as the constituents of concrete by replacing or partially replacing the cement or aggregates which makes it cost effective and also conserves the natural resources. Concrete is the important material in construction other than steel and timber and its main constituents are cement, sand, fine and coarse aggregates, and water. But, one of the greatest environmental concerns in construction industry are the production of

cement which emits large amount of CO_2 to the atmosphere. It is estimated that production of one ton of clinker/cement releases equally one ton of CO_2 . Therefore, the past two decades of research is diverted primarily in making concrete without cement or at least partially in low or high volumes, replacing cement by suitable alternatives like fly ash, silica fume, ground granulated blast furnace slag, rice husk ash. China, India, united states of America is the order of countries having largest cement consumption.

E-waste describes as loosely thrown-out, not needed any more, no longer useful/no longer used, broken, electrical or electronic devices. Fast technology change, low initial cost has resulted in a fast growing of electronic waste around the globe. Several

tons of E-waste need to be disposed per year. Traditional place where garbage and trash is dumped method is not a related to surrounding conditions or the health of the Earth friendly solution and the disposal process is also very complicated. How to reuse the non-disposable E-waste becomes an important research topic. The processing of electronic waste causes serious health and pollution Problems due to electronic equipment contains serious contaminants such as lead, Cadmium, Beryllium, Poisonous metal, Mercury, Nickel, Silver, Zinc. In India, E-waste is mostly generated in large cities like Delhi, Mumbai and Bangalore. In these cities a complex e-waste handling infrastructure has developed mainly based on a long tradition of waste recycling. Sixty five cities in India generate more than 60% of the total e waste generated in India. Ten states generate 70% of the total E-waste generated in India. Because of increment in cost of typical coarse aggregate it has constrained the civil engineers to discover appropriate other options to replace it. E-waste can be utilized as one such option for coarse aggregate. Owing to shortage of coarse aggregate for the planning of solid, incomplete supplanting of E-waste with coarse aggregate was tried.

1.2 E-waste

E-waste refers to electronic products nearing the end of their “useful life” for example, computers, televisions, VCRs, stereos, copiers, and fax machines. Many of these products can be reused, refurbished, or recycles. In this project these e-waste were crushed and used in the place of 20mm coarse aggregate.

1.2 Marble dust is obtained from “cutting and manufacturing industries of marble”. In India near about 3,500 metric tons of marble dust slurry per day is generated. So, Marble dust is very easily available with very less cost. Some of industries used to wash out this marble powder with water in natural streams which cause water pollution and is harmful for our environment. So, it is advisory to use marble dust as partial replacement with cement as it has properties similar to cement and one of good pozzolanas.

2. LITERATURE REVIEW

Sunil Ahirwar et.al The waste materials that come from the construction field can also be reused that gives better economic and environmental benefit. Sunil Ahirwar along with his colleagues tried to make the best out of e-waste as they inappropriately found rapid disposal of Electronic-waste. So, they tried the including the e-waste into coarse aggregate replacement. The aim of their study was the investigation of the change in mechanical Behaviour & Properties of concrete when the addition of E-Waste is done in concrete. The Coarse aggregate is replaced partially by E-waste in 0% to 30% proportions. They also included 10, 20, and 30 Percent of flyash partially replacing the cement. As per the tests conducted on various specimens made with different percentage inclusions of e-waste and fly ash as partial replacement of coarse aggregate and cement respectively, they have come to results: 30% of cement replacement with fly ash along with electronic waste gives the best result. The strength of concrete increased by 17.8% by the inclusion of 7.5% e-waste. Many favorable results were

obtained like concrete is lightweight and thus the weight of the structure is reduced. Workability was increased as increase in percentage inclusion of e-waste. Makes concrete more flexible and hence bear seismic loads. They concluded that E- waste can be used replace the coarse aggregate somewhere between 10 – 20%.

Manikandan et.al Manikandan along with his team focused on the improper disposal of e-waste. In our Country (India), primary source of Electronic waste generated was from public & private sector which are 70% from the total waste being generated. The annually estimated generation of E-waste was around 4,00,000 tons. It is found that most of the e-waste generated is from cities like Bombay, Delhi, Bengaluru, and Madras was estimated approx. 10,000 , 9,000, 8,000 ,and 6,000 Tonnes Respectively. only 4% of total waste generated is recycled per annum, it's a disappointment. So, they made efforts for usage of E-waste components as for partially replacing the coarse(10-12) mm Aggregate. The major conclusions drawn by them are: Density of Electronic Waste as Replacement of Coarse or Fine Aggregate in concrete is less when compared to Existing Normal or Conventional concrete as resulting in the lightweight blocks emerge which also reduced the cost of concrete blocks. Up to 15% replacement is allowable as it increased compressive strength and durability compared to conventional concrete.

2.3 Objective of the study

The present study deals with the replacement of coarse aggregate with E-waste in the range of 0%, 5%, 10%, 15%, 20%, 25%, 30%, 35% and replacement of

cement with marble powder by 15% in the preparation of M20 grade concrete mix.

1. To study the effect of adding different percentages of coarse aggregates replacement with E-Waste (0%, 5%, 10%, 15%, 20%, 25%, 30%, 35%) and 15% cement replacing with marble powder.
2. To determine the workability of freshly prepared concrete by Slump Test.
3. To determine the compressive strength of cubes at 7, 14, 28 days curing

3. EXPERIMENTAL WORK

3.1 Materials Used

- Cement
- Coarse Aggregates
- Fine aggregates
- Water
- E waste (Electronic waste)
- Marble dust

Cement

Cement used in the investigation was found to be Ordinary Portland Cement (53 grade) confirming to IS: 12269 – 1987.

Table. 1: Physical properties of cement.

Property	Result
Standard Consistency	34%
Initial Setting Time	41min
Final Setting Time	315min
Specific gravity	3.10

Aggregates

Coarse aggregates: The coarse aggregate used is from a local crushing unit having 20mm nominal size. The coarse aggregate conforming to 20mm well-graded according to IS:383-1970 is used in this investigation.

Fine aggregates: The fine aggregate used was obtained from a nearby river course. The fine aggregate conforming to zone – II according to Is 383-1970 was used.

Table .2: Physical properties of fine aggregates & coarse aggregates.

Property	CA	FA
Water absorption	0.7%	0.3%
Specific gravity	2.67	2.55
Impact value	8%	-
Crushing value	14.21%	-

Water

Water is an important ingredient of concrete as it participates in the chemical reaction with cement. Water cement ratio used in the mix is 0.50.

E – Waste (Electronic waste)

E-waste refers to electronic products nearing the end of their “useful life” for example, computers, televisions, VCRs, stereos, copiers, and fax machines. Many of these products can be reused, refurbished, or recycled. In this project this e-waste were crushed and used in the place of 20mm coarse aggregate.

Table .3 Physical properties of E – waste.

Properties	Values
Water absorption	0.04
Specific gravity	1.21
Crushing value	2.35%

Marble dust

Marble Powder is obtained from the transformation of pure limestone. The purity of marble depends upon the color of the marble. Since the ancient times, marble is widely used in monuments and historical buildings for decorative purpose. In India, tonnes of marble waste has been produced from the industries. But there are some impurities present in the waste that cannot be easily deposited off. Such type of impurities mixed with soil and water. When they mixed with soil it reduces the porosity and permeability of the soil. Also, if it mixes with water it pollute the water and make the water unfit for use. So, it is necessary to use the waste in functional manner.

Table. 4: Physical properties of marble powder.

Property	Value
Specific gravity	3.06
Fineness value	3%

3.2 METHODOLOGY

For this research project ordinary Portland cement of grade 54, river sand is used as fine aggregate, natural crushed aggregate is used as a coarse aggregate and crushed e-waste plastic of which is passed from 20 mm sieve and retained on 4.75 mm sieve is employed in this research project. As per IS 10262:2019 mix design is done. M20 mix prepared which contain 0% to 35% electronic waste as partial replacement to coarse aggregate along with this 15% Marble dust as a partial replacement of Cement. Once design of mix has been prepared then 150*150*150mm cubes is casted for these mixes, 9 cubes for each mix is casted which is going to tested after 7,14 and 28 days of curing i.e. total 81 cubes is casted.

3.3 Mix design

3.3.1 Mix Proportions

M20 grade of concrete is considered. Natural coarse aggregate is replaced with E-Waste with various percentages 0%, 5%, 10%, 15%, 20%, 25%, 30% & 35%. Cement is replaced with marble dust by 15%. The mix design for concrete is carried out as per IS 10262. Details of mix proportion for M20 concrete given below:

Table. 5: Individual weight of materials M20 grade.

Item name	For 1 cube (gms)
Cement	1496.88
Fine aggregates	2494.8

Coarse aggregates	5613.3
water	748.44

3.3.2 Mixed design proportions for Marble dust & E-Waste Concrete

- In this research work 15 Standard cubic specimens of size 150mm (nine sample for each percentage) were casted for the compressive strength of concrete and it was kept under curing for 7, 14 days & 28 days of age. Total cubes for compressive strength testing was 81 (9 cubes * 9 proportions).
- Mass of ingredients required will be calculated for 9 no's cubes assuming 10% wastage
- Volume of the Cube = $9 * 1.10 * (0.15)^3 = 0.0334125 \text{ m}^3$

Table. 6: Material proportions cubes (M20).

MP - Ewaste	0%-0%	15%-0%	15%-5%	15%-10%	15%-15%	15%-20%	15%-25%	15%-30%	15%-35%
Cement (Kgs)	15.47 12	11.45 052	11.45 052	11.45 052	11.45 052	11.45 052	11.45 052	11.45 052	11.45 052
Marble powder (kg)	0	2.020 68	2.020 68	2.020 68	2.020 68	2.020 68	2.020 68	2.020 68	2.020 68
water (lit)	7.409 556	7.409 556	7.409 556	7.409 556	7.409 556	7.409 556	7.409 556	7.409 556	7.409 556
Fine aggregate (Kgs)	22.45 32	22.45 32	22.45 32	22.45 32	22.45 32	22.45 32	22.45 32	22.45 32	22.45 32
E-waste (kg)	0	0	2.523 9	5.051 97	7.577 955	10.10 394	12.62 99	15.15 59	17.68 189
Coarse aggregate (Kgs)	50.51 97	50.51 97	47.99 38	45.46 773	42.94 17	40.41 57	37.88 98	35.36 38	32.83 781

3.3.3 Sample Production

The cement, fine and coarse aggregates were weighted according to mix proportion of M₂₀. All are mixed in a bay until mixed

properly and water was added at a ratio of 0.5. The water was added gradually and mixed until homogeneity is achieved. Any lumping or balling found at any stage was taken out, loosened and again added to the mix.

For the second series of the mixture, the marble dust was added at 5%, 10%, 15%, 20%, 25%, 30% and 35% by weight of coarse aggregates and the marble dust was added 15% by the weight of cement. Immediately after mixing, slump test was carried out for all the concrete series mixture. A standard 150×150×150mm cube specimen were casted.

The samples were then stripped after 24hours of casting and are then be ponded in a water curing. As casted, a total of (91) 150×150×150mm cubes specimens were produced.

3.3.4 Curing

The method of curing adopted was the ponding method of curing and produced samples were cured for cubes at 7days, 14days, 28 days and beams at 28days.

3.4 Test for Fresh Properties of Concrete (Workability Test)

Slump Test

which can be employed either in laboratory or at site of work. It is not a suitable method for very wet or very dry concrete. It does not measure all factors contributing to workability, nor is it always representative of the placability of the concrete. It is not a suitable method for very wet or very dry concrete. It does not measure all factor contributing to workability. The slump test

was carried in accordance with B.S:1882 PART2:1970.

3.5 Test for Harden Properties of Concrete

Compressive Strength of Concrete (IS 516-1959)

The compression test was conducted according to IS 516-1959. This test helps us in determining the compressive strength of the concrete cubes. The obtained value of compressive strength can then be used to assess whether the given batch of that concrete cube will meet the required compressive strength requirements or not. For the compression test, the specimen's cubes of 15 cm x 15 cm x 15 cm were prepared by using hwa concrete as explained earlier. These specimens were tested under universal testing machine after 7 days, 14 days and 28 days of curing. Load was applied gradually at the rate of 140kg/cm² per minute till the specimens failed. Load at the failure was divided by area of specimen and this gave us the compressive strength of concrete for the given sample.

4. RESULTS AND DISCUSSIONS

4.1 Comparative graphs for E-waste and Coarse aggregates

The results for material test on, water absorption test, specific gravity test, aggregate crushing value test, aggregate impact value test are given below.

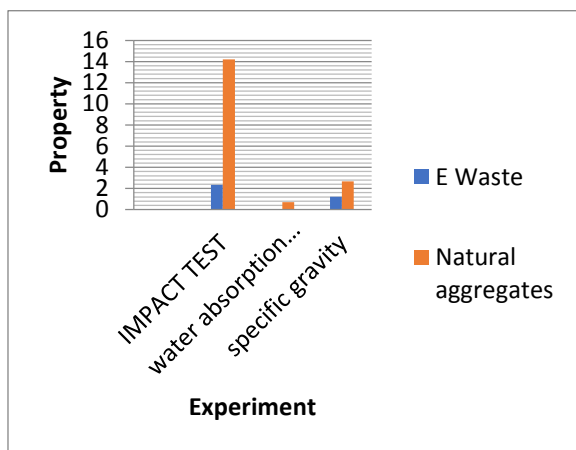


Fig. 1: Aggregates and E waste comparison with testing.

From the above graph, it observe that the mechanical properties (Crushing & Impact value) of e waste more than normal natural aggregates. The water absorption value of E- waste approximately zero.

4.2 Fresh Properties of Concrete

Slump Test

The Slump test was performed on the E-Waste & Marble concrete to check the workability of it at different replacements viz. 5 % - 35% by coarse aggregates and 15% by Cement, the following results were obtained, according to which it can be concluded that with the increase in % E - Waste from 0 to 35 % , workability increases. The results obtained for Slump test are shown below in Table 7.

Table. 7: Results of slump test.

Mix	Marble dust% - Ewaste%	Slump value (cm)
M1	0% - 0%	60
M2	15% - 0%	70
M3	15% - 5%	73

M4	15% - 10%	77
M5	15% - 15%	82
M6	15% - 20%	84
M7	15% - 25%	87
M8	15% - 30%	90
M9	15% - 35%	95

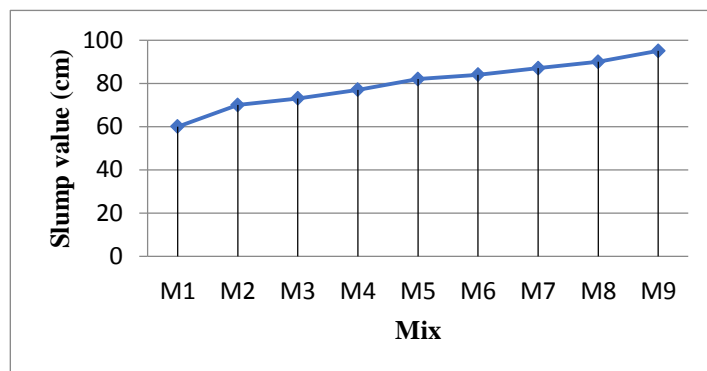


Fig. 2: Slump test results.

The above fig. 2 shows the slump results. It was observed that, the slumps increases as the E-WASTE content were increased in the mix.

4.3 Harden properties of concrete

Compressive Strength Test

The compressive strength test was performed on the cubes of size 15 cm x 15 cm x 15 cm to check the compressive strength of E - Waste & MD concrete and the results obtained are given in Table 8.

Table. 8: Results of compressive strength test.

Mix	Marble dust% - Ewaste %	Compressive strength of cubes (Average results)		
		7 days (N/mm ²)	14 days (N/mm ²)	28 days (N/mm ²)
M1	0% - 0%	15.32	20.1	24.2
M2	15% - 0%	17.57	22.86	26.45
M3	15% - 5%	17.02	22.57	25.98
M4	15% - 10%	16.53	21.21	24.31
M5	15% - 15%	14.95	19.48	22.92
M6	15% - 20%	12.68	17.72	20.43
M7	15% - 25%	11.21	15.37	18.23
M8	15% - 30%	9.32	13.82	16.43
M9	15% - 35%	8.5	12.68	15

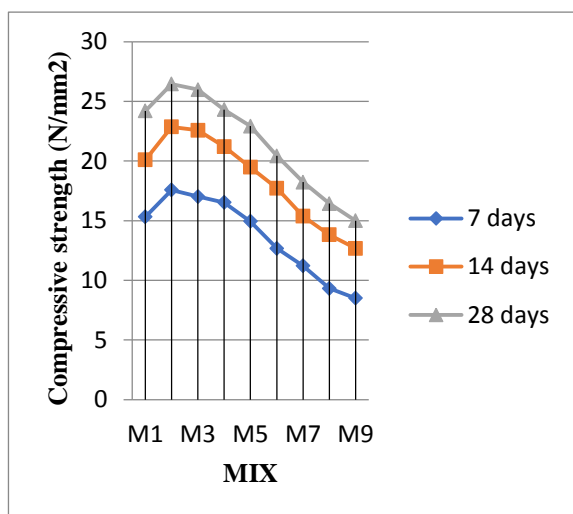


Fig. 3: Compressive strength v/s mix.

From the above results it was observed that with the increase in percentage of E-Waste from 5% and 10% in concrete the compressive strength more than control mix (M1).

5. CONCLUSIONS

From the above study following conclusions are drawn-

1. The Compressive Strength of E-waste concrete with 10% replacement as coarse aggregate and 15% replacement as cement is higher than that of control mix concrete (M1).
2. The Flexural Strength of E-waste concrete with 10% replacement as coarse aggregate and 15% replacement as cement is higher than that of control mix concrete (M1).
3. The workability increases as the E-WASTE (fixed 15% Marble dust replacement by cement) content were increased in the mix.
4. E-waste can effectively been used as construction materials and its mechanical properties are greater then that of natural coarse aggregates. The Water absorption value of E waste is approximately zero.
5. The use of E-waste in concrete is possible to improve its mechanical properties and can be one of the economical ways for their disposal in environment friendly manner.
6. The concept of replacement of E-waste and Marble dust in concrete would be environment friendly and reduces the disposal of E-waste in landfills.

REFERENCES

- [1] IJSTE-International Journal of Science Technology and Engineering Sunil Ahirwar: ((MTech scholar, dept. of civil Eng.-millennium institute of technology, Bhopal).
- [2] Jr. of Industrial Pollution Control (Research article) Manikandan M (SRM University Chennai).
- [3] The International Journal of Engineering and Science (IJES) Sagar R. Raut (Department of Civil Engineering, Jagadambha College of Engineering & Technology, Yavatmal).
- [4] R Lakshmi, S Nagan - International journal of environmental ..., 2010 - indianjournals.com.
- [5] Green high strength concrete containing recycled Cathode Ray Tube Panel Plastics (E-waste) as coarse aggregate in concrete beams for structural applications. Author links open overlay panel K.Hamsavathia K. SooryaPrakashb V.Kavimanic.
- [6] P. Krishna Prasanna, M. Kanta Rao, "Strength Variations in Concrete by Using E-Waste as Coarse Aggregate", International Journal of Education and Applied Research, Volume 4, Issue Spl 2, June 2014.
- [7] Concrete blends with E-waste plastic for sustainable future Needhidasan Santhanam, B. Ramesh, Freddy Khim Pohsnem Department of Civil Engineering, Saveetha School of Engineering, Saveetha Institute of Medical and Technical Sciences, Chennai, India.
- [8] The amalgamation of E-waste plastics in concrete with a superplasticizer for better strength S. Needhidasan, C.R. Vigneshwar, B. Ramesh. Department of Civil Engineering, Saveetha School of Engineering, Saveetha Institute of Medical and Technical Sciences, Chennai, India.
- [9] Experimental study on the use of E-waste plastics as coarse aggregate in concrete with manufactured sand Santhanam Needhidasan, B. Ramesh, S. Joshua Richard Prabu Department of Civil Engineering, Saveetha School of Engineering, Saveetha Institute of Medical and Technical Sciences, Chennai, India.
- [10] Demonstration on the limited substitution of coarse aggregate with the E-waste plastics in high strength concrete Needhidasan, Puli Sai.
- [11] A Review Paper on Use of E-Waste in Concrete Sohan Lal Angure1 Dr. Savita Maru2 1PG Student (Computer Aided Structural Designing & Drafting) 2Professor 1,2Department of Civil Engineering 1,2Ujjain Engineering College Ujjain M.P. India.
- [12] ISSN: 2454-132X Impact factor: 4.295 (Volume 4, Issue 3) Available online at www.ijariit.com Replacement of fine aggregate with plastic in concrete
- [13] Nagajothi, P. Gomathi, and T. Felixkala. "Compressive Strength of Concrete Incorporated with E-fiber Waste." Beams. Journals of Structural Engineering, ASCE, 125(6), 653-660.

- [14] Mrs. Kaleeswari. G Dr.
Dhanalakshmi. G, Study on Marble
Powder as Partial Replacement of
Cement in Concrete, GRD Journals
June 2017