

Base Fluid Effect on the Viscosity of Nanofluid Suspended with Silicon Carbide nanoparticles

Kanthimathi Tumuluri¹,

¹Department of Mechanical Engineering, Koneru Lakshmaiah Education Foundation, Vaddeswaram Green Fields Guntur Dt., Andhra Pradesh, 522302, India

Bhramara P²

²Department of Mechanical Engineering, Jawaharlal Nehru Technological University, Kukatpally, Telangana, 500085, India

Abstract.

Nanofluids are potential heat transfer fluids due to the flexibility associated with the customization of thermophysical properties. In the present paper, the effect of working fluid on the viscosity of Silicon Carbide (SiC) nanoparticle suspensions is determined experimentally at temperature of 40, 45 and 50°C. Three different working fluids, viz., Distilled Water (DW), a mixture of Ethylene glycol and Distilled water in the ratios of 20:80 and 40:60 (20:80 EG-DW and 40:60 EG-DW) are considered to prepare SiC nanofluid in the particle fraction ranging from 0.02% to 0.08% by volume. For the same particle concentrations of SiC suspensions, a significant enhancement in viscosity is observed. Both EG-DW based nanofluids have exhibited higher viscosity than that of water-based nanofluid. The viscosity of SiC/40:60 EG-DW nanofluid is 2.12 times higher than SiC/DW and 1.27 times higher than SiC/20:80 EG-DW nanofluid for 0.08% particle concentration by volume and at the operating temperature of 45°C.

Keywords: nanoparticle, nanofluid, particle concentration, viscosity

1. Introduction

In the past few decades, nanofluids have gained significance as the new class of working fluids with superior thermophysical as well as transport properties. Vasu et al. [12, 13] conducted an analytical research to develop correlations for the thermophysical properties and Nusselt number of water based Al₂O₃, Cu, CuO and TiO₂ nanofluids, Propylene glycol-

water [14, 3, 5] on the heat transfer performance of different nanofluids. In order to improve the heat transfer enhancement most of the researchers have conducted study on the improvement in the design of heat exchangers [8, 10]. Humenic et al. [4] experimentally investigated the thermo-physical properties and heat transfer enhancement of Water based SiC nanofluid using a two-phase closed-loop thermosyphon for particle concentration of 0.5% and 1% by volume within the temperature range of 20°C to 50°C. Maximum heat transfer enhancement of 24.4% was reported at a 1% particle concentration by volume for the maximum temperature difference. Li et al.[6] experimentally investigated the thermo-physical properties of 40:60 EGW based SiC nanofluids in the particle concentration ranging from 0.1 to 0.5% by volume for the temperatures ranging from 10 to 50°C. Based on their experimental results a maximum of 53.81% enhancement was obtained in thermal conductivity at 0.5% particle concentration by volume and at 50°C. Nikkam et al. [7] experimentally investigated the thermophysical properties of water-based and 50:50 EGW based SiC nanofluids for weight percentage of 3%, 6% and 9% concentrations at 20°C. They reported a maximum enhancement of 15.2% and 20% in thermal conductivity and maximum enhancement of 22.7% and 14% in viscosity for SiC/Water and SiC/50:50 EGW nanofluids respectively at 9% particle concentration by weight. Results revealed that the average enhancement in the heat transfer coefficient was about 13% for SiC/50:50 EGW nanofluid when compared with 50:50 EGW base fluid. Timofeeva et al. [11] experimentally determined the effect of temperature and base fluid on the heat transfer characteristics of SiC/50:50 EGW and SiC/Water nanofluids. The experiments were carried out in the Reynolds number range of 4500 to 7500 for a particle concentration of 4% by volume for temperatures ranging from 57°C to 71°C for different particle sizes ranging from 16nm to 90nm. Their results reported a maximum enhancement of 14.2% in the heat transfer coefficient for 90 nm SiC/50:50 EGW at 71°C whereas the enhancement of water-based SiC nanofluid is very less compared to EGW based SiC nanofluid. Azmi et al. [1] experimentally investigated the forced convection heat transfer of Al₂O₃ nanoparticles suspended in Water and Ethylene Glycol mixture in the volume ratio 60:40, 50:50, and 40:60. The particle concentration considered by them are in the range of 0.2% to 1% for operating temperatures of 30, 50 and 70°C under the Reynolds number range of 3000 to 25000. They reported that at the higher operating temperature of 70°C, the maximum heat transfer enhancement obtained was 24.6%

for 60:40 W-EG based Al_2O_3 nanofluid, 24.2% for 40:60 W-EG based nanofluid and 19% for 50:50 W-EG based Al_2O_3 nanofluid. They concluded that the variation in temperature and thermophysical properties of the base mixtures greatly influence the heat transfer coefficient of nanofluids. The heat transfer characteristics of nanofluid majorly depends on the thermal conductivity and viscosity of the nanofluids.

In the present paper, the effect of base fluid on the viscosity of SiC nanofluids is studied experimentally. The base fluids considered are Demineralized Water (DW), mixture of Ethylene Glycol and Distilled Water in the volume ratios of 20:80 and 40:60 (20:80 EG-DW and 40:60 EG-DW). The SiC nanoparticles are suspended in the base fluids in the fractions of 0.02%, 0.04%, 0.06% and 0.08% by volume at temperatures 40, 45 and 50°C.

2. Preparation of Nanofluids

SiC nanoparticles are procured from Nano amor Texas USA. The average particle size of the SiC nanoparticles is tested using TEM images shown in Figure 1, the size of the nanoparticles is approximately 50 nm.

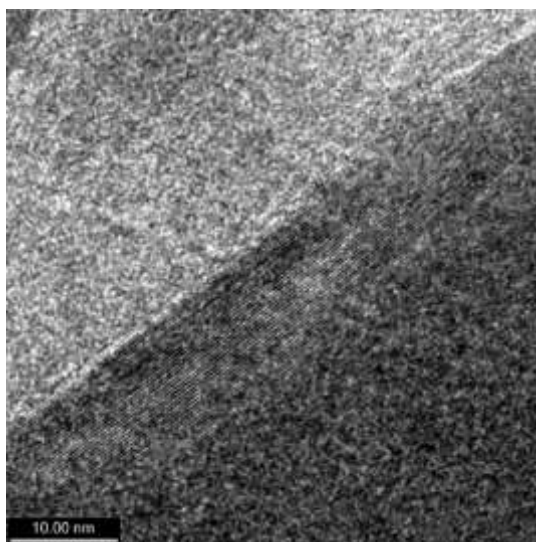


Figure 1. TEM Image of SiC nanoparticles

The SiC nanoparticles are mixed in three different base fluids viz., Distilled water, 20:80 EG-DW, and 40:60 EG-DW in the particle concentrations of 0.02%, 0.04%, 0.06% and 0.08% by volume. Surfactant is not used in the preparation of nanofluid as its presence affects the original properties of nanofluids. The weight of nanoparticles to be mixed in each base fluid is evaluated using Eq. (1), where ϕ is the particle concentration by volume of the nanofluid.

$$\phi = \frac{\frac{m_{np}}{\rho_{np}}}{\left(\frac{m_{np}}{\rho_{np}} + \frac{m_{bf}}{\rho_{bf}}\right)} \times 100 \quad (1)$$

Stable nanofluids are prepared by two step method, the nanoparticles are suspended in the required concentration in the base fluids and are stirred continuously using Probe sonicator shown in Figure 2 for about 4 to 6 hours depending on the particle concentration.



Figure 2. Probe Sonicator

The stability of the nanofluids prepared is tested by measuring Zeta Potential. The Zeta potential obtained for all the concentrations considered is greater than -30mV indicating the better stability of the nanoparticles in the base fluid. The viscosity of SiC nanoparticle suspensions in DW, 20:80 EG-DW, and 40:60 EG-DW is measured using the DV2T Viscometer shown in Figure 3, for different particle concentration ranging from 0.02 to 0.08% by volume. The viscosity of these nanofluids is measured at a temperature of 40, 45 and 50°C.



Figure 3 DV2T Brookfield Viscometer

3. Results and Discussion

Viscosity is one of the important properties of nanofluids as it accounts for the momentum transfer leading to the pressure drop and frictional losses in the flow, thus affecting the pumping power. The measured viscosity values are compared with Sharma et al. [9] and Corcione [2] correlations. The Corcione [2] and Sharma et al. [9] correlations are given by Eqs. (2) and (3), respectively.

$$\frac{\mu_{nf}}{\mu_{bf}} = \frac{1}{1 - 34.87 \left(\frac{d_p}{d_{bf}}\right)^{-0.3} \left(\frac{\phi}{100}\right)^{1.03}} \quad (2)$$

Where d_{bf} is the molecule equivalent diameter of the base fluid given by

$$d_{bf} = 0.1 \left[\frac{6M}{N\pi\rho_{bf0}} \right]^{1/3} . M \text{ is molecular weight of base fluid, } N \text{ is the Avogadro number and}$$

ρ_{bf0} is the density of base fluid at 20°C.

$$\frac{\mu_{nf}}{\mu_{bf}} = \left[\left(1 + \frac{\phi}{100}\right)^{11.3} \left(1 + \frac{T_{nf}}{70}\right)^{-0.038} \left(1 + \frac{d_p}{170}\right)^{-0.061} \right] \quad (3)$$

The measured and predicted values of viscosity of DW, 20:80 EG-DW and 40:60 EG-DW based SiC nanofluids at 40, 45 and 50°C are represented in Figure 4, 5 and 6 respectively

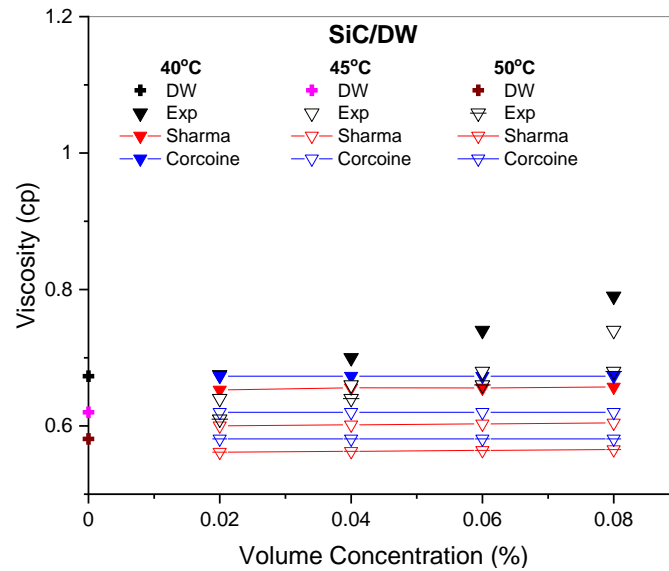


Figure 4. Viscosity of SiC/DW Nanofluid

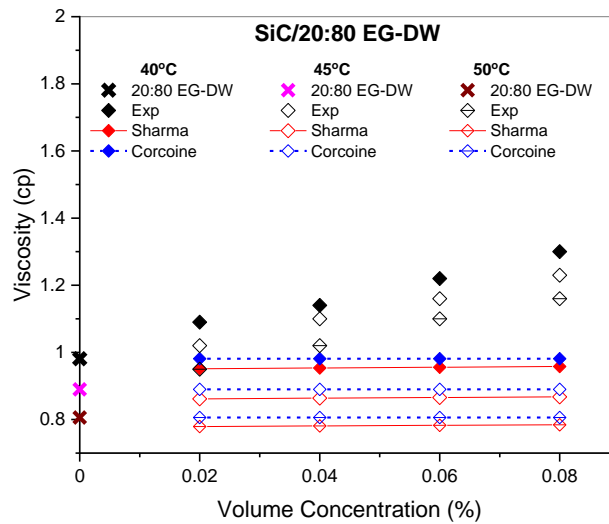


Figure 5. Viscosity of SiC/20:80 EG-DW Nanofluid

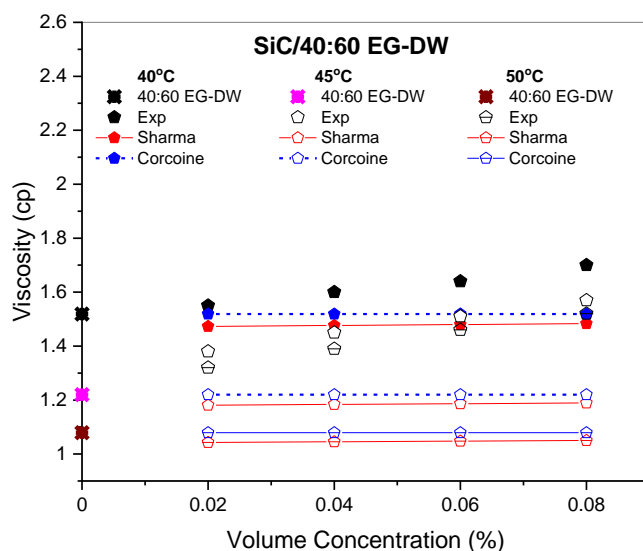


Figure 6. Viscosity of SiC/40:60 EG-DW Nanofluid

Both EG-DW based nanofluids have exhibited higher viscosity than that of water-based nanofluid, with the viscosity being increased with the increase of EG percentage in the base fluid. The percentage increment in the viscosity of DW, 20:80 EG-DW and 40:60 EG-DW based SiC nanofluids compared to that of their respective base fluid varies from 3.22% to 19.35%, 14.6% to 38.2%, 13.11% to 28.68% respectively as the particle concentration by volume varies from 0.02% to 0.08% at 45°C, similar trend was observed for 40 and 50°C. The correlations considered not only underestimated the experimental values but also could not capture the effect of particle loading on viscosity. Comparison of the viscosities of SiC nanofluids at 45°C in the 3 different base fluids is shown in Figure 7 and the relative viscosity is shown in Figure 8.

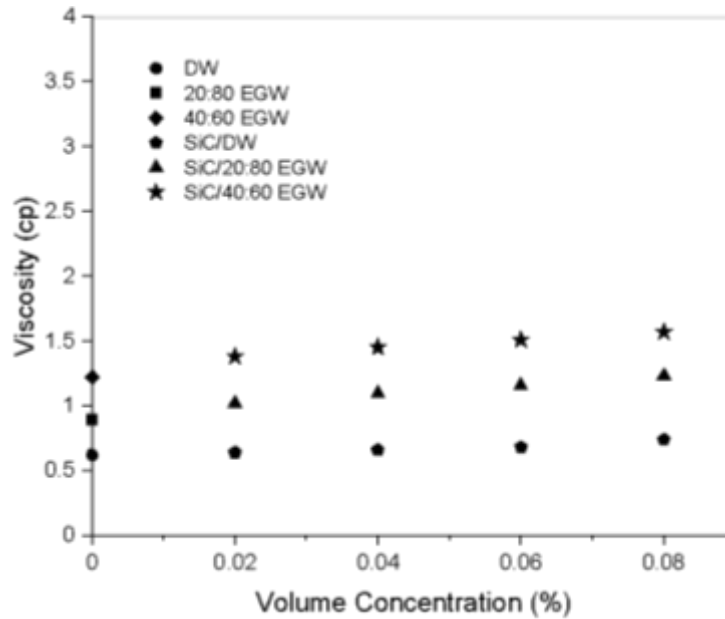


Figure 7. Comparison of viscosities of SiC nanofluid in 3 different base fluids

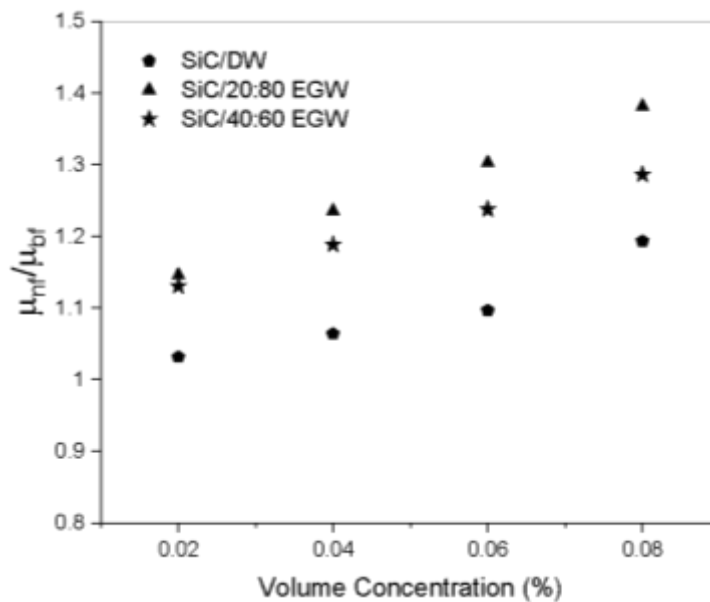


Figure 8. Relative Viscosity of SiC nanofluids in 3 different base fluids

The viscosity of SiC/40:60 EG-DW nanofluid is 2.12 times higher than SiC/DW and 1.27 times higher than SiC/20:80 EG-DW nanofluid for 0.08% particle concentration by volume and at the operating temperature of 45⁰C. It is observed that though the viscosity of

40:60 EG-DW based SiC nanofluid is higher than 20:80 EG-DW and DW based nanofluids the relative viscosity of 20:80 EG-DW is greater than 40:60 EG-DW based SiC nanofluid. This decrease in the relative viscosity of the 40:60 EG-DW based nanofluid is due to the increase in the viscosity of the base fluid. This indicates the impact of base fluid plays a major part in the viscosity of nanofluids.

4. Conclusions

The viscosity of DW, 20:80 EG-DW, and 40:60 EG-DW based SiC nanofluids is experimentally investigated for low particle concentration of 0.02% to 0.08% by volume at temperatures 40, 45 and 50°C. It is observed that the viscosity of the nanofluids increase with increase in the particle concentration and decreased with the increase in temperature. EG-DW based SiC nanofluids exhibited greater viscosity values than DW based nanofluids. Higher viscosity values were obtained for 40:60 EG-DW based nanofluid which is 2.12 times greater than DW and 1.27 times greater than 20:80 EG-DW based nanofluids. Though the viscosity values of 40:60 EG-DW is greater than 20:80 EG-DW based SiC nanofluids, the relative viscosity of 20:80 EG-DW based SiC nanofluid is found to be greater than 40:60 EG-DW based nanofluids indicating the effect of base fluid. Hence, it is observed that the base fluids chosen for the preparation of the nanofluids are having greater impact on viscosity of nanofluids and the combination of nanoparticle and base fluid also pays a major role on the viscosity of nanofluids.

Acknowledgements

I am grateful to my guide Dr. P.Bhramara, who guided me throughout the project.

References

1. Azmi, W. H., N. A. Usri, RizalmanMamat, K. V. Sharma, and M. M. Noor, 2017. Force convection heat transfer of Al₂O₃ nanofluids for different based ratio of water: ethylene glycol mixture. Applied Thermal Engineering, 112, pp: 707-719. <http://dx.doi.org/10.1016/j.applthermaleng.2016.10.135>

2. Corcione, M. 2011, "Empirical correlating equations for predicting the effective thermal conductivity and dynamic viscosity of nanofluids"; *Energy conversion and management*; vol. 52(1), pp.789-793.
3. Dittus, Frederick William, 1930. Heat Transfer in Automobile Radiators of the Tubler Type. Univ. Calif. Pubs. Eng. **2**, pp: 443-461.
4. Huminic, Gabriela, Angel Huminic, ClaudiuFleaca, Florian Dumitrache, and Ion Morjan, 2017. Thermo-Physical Properties of Water-Based SiC Nanofluids for Heat Transfer Applications. *International Communications in Heat and Mass Transfer*, 84, pp:94-101. <http://dx.doi.org/10.1016/j.icheatmasstransfer.2017.04.006>
5. Kumar Sai Tejas P., Appalanaidu Y, 2017. Experimental investigation of convective heat transfer augmentation using ZnO-propylene glycol nanofluids in an automobile radiator. *International Journal of Mechanical Engineering and Technology*, 8(7), pp: 1132-1143
6. Li, Xiaoke, ChangjunZou, and Aihua Qi, 2016. Experimental Study on the Thermo-Physical Properties of Car Engine Coolant (water/ethylene glycol mixture type) Based SiC Nanofluids. *International Communications in Heat and Mass Transfer*, **77**, pp:159-164. <http://dx.doi.org/10.1016/j.icheatmasstransfer.2016.08.009>[10.1016/j.applthermaleng.2015.07.004](http://dx.doi.org/10.1016/j.applthermaleng.2015.07.004)
7. Nikkam, Nader, Ehsan B. Haghghi, MohsinSaleemi, MohammadrezaBehi, RahmatollahKhodabandeh, Mamoun Muhammed, Björn Palm, and Muhammet S. Toprak, 2014. Experimental Study on Preparation and Base Liquid Effect on Thermo-Physical and Heat Transport Characteristics of α -SiC Nanofluids. *International Communications in Heat and Mass Transfer*, **55**, pp:38-44. <http://dx.doi.org/10.1016/j.icheatmasstransfer.2014.04.011>
8. Rao P.D., Nageswara Rao B, 2017. CFD simulations and validation through test data of a double pipe counter flow heat exchanger. *International Journal of Mechanical Engineering and Technology*, 8(5), pp.818-831

9. Sharma, K. V., Sarma, P. K., Azmi, W. H., Mamat, R., & Kadirgama, K, 2012. Correlations to predict friction and forced convection heat transfer coefficients of water based nanofluids for turbulent flow in a tube. *International Journal of Microscale and Nanoscale Thermal and Fluid Transport Phenomena*, 3(4), pp. 1-25.
10. Sarma P.K., Konijeti R., Subramanyam T., Prasad L.S.V., Korada V.S., Srinivas V., Vedula D.R., Prasad V.S.R.K, 2017. Fouling and its effect on the thermal performance of heat exchanger tubes. *International Journal of Heat and Technology*, 35(3), pp: 509-519. DOI: 10.18280/ijht.350307
11. Timofeeva, Elena V., Wenhua Yu, David M. France, Dileep Singh, and Jules L. Routbort, 2011. Base Fluid and Temperature Effects on the Heat Transfer Characteristics of SiC in Ethylene Glycol/H₂O And H₂O Nanofluids. *Journal of Applied Physics*, **109**, pp:1-5. <http://dx.doi.org/10.1063/1.3524274>
12. Vasu, V., K. Rama Krishna, and A. C. S. Kumar, 2007. Analytical prediction of forced convective heat transfer of fluids embedded with nanostructured materials (nanofluids). *Pramana J-Physics*, 69(3), pp:411-421. <https://doi.org/10.1007/s12043-007-0142-1>
13. Velagapudi, Vasu, Krishna Rama Konijeti, and Kumar Sekhara Chandra Aduru, 2008. Empirical correlations to predict thermophysical and heat transfer characteristics of nanofluids. *Thermal Science*, 12(2), pp:27-37. <https://doi.org/10.2298/TSCI0802027V>
14. Vijaya Sagar T., Appalanaidu Y, 2017. Experimental investigation of heat transfer coefficient and friction factor in a double pipe heat exchanger with and without twisted tape inserts using ZnO-propylene glycol nanofluid. *International Journal of Mechanical Engineering and Technology*, 8(8), pp: 94-106.